

Remigiusz Romankiewicz, Ferdynand Romankiewicz

Influence of time on modification effect of silumin AlSi11 with strontium and boron

Wpływ czasu na efekt modyfikacji siluminu AlSi11 strontem i borem

Abstract

Studies on the effect of time on the modification of AlSi11 silumin with variable strontium micro additives in the form of an AlSr10 master alloy and boron in an AlB4 master alloy were investigated. The results showed that the strontium micro additive resulted in a satisfactory improvement in the $\alpha(\text{Al}) + \beta(\text{Si})$ eutectic and an increase in tensile strength (R_m) and unit elongation (A_5); this is also the case two hours after adding the modifier. The simultaneous modification of silumin with AlB4 and AlSr10 causes a strong fragmentation of the alloy grains and significant improvement in R_m and A_5 (also two hours after adding the modifiers).

Keywords: silumin, modification, structure, mechanical properties

Streszczenie

Przeprowadzono badania nad wpływem czasu na modyfikację siluminu AlSi11 zmiennymi mikrodotkami strontu w postaci zaprawy AlSr10 oraz boru w postaci zaprawy AlB4. Wyniki badań wykazały, że mikrodotek strontu powoduje zadowalające uszlachetnienie eutektyki $\alpha(\text{Al}) + \beta(\text{Si})$ i wzrost wytrzymałości na rozciąganie (R_m) oraz wydłużenia względnego (A_5), także po upływie dwóch godzin po dodaniu modyfikatora. Równoczesna modyfikacja siluminu zaprawami AlB4 i AlSr10 powoduje silne rozdrobnienie ziarn stopu i istotną poprawę R_m oraz A_5 , również po upływie dwóch godzin po dodaniu modyfikatorów.

Słowa kluczowe: silumin, modyfikacja, struktura, właściwości mechaniczne

1. Introduction


The properties of Al-Si cast alloys depend on the state of their structures. The decisive influence on them affect the shape, size, and distribution of the components of the structure. The properties in hypoeutectic alloys are determined by the size and shape of the primary phase $\alpha(\text{Al})$ and the morphology of the eutectic $\alpha(\text{Al}) + \beta(\text{Si})$. The closer the

content of silicon is to the eutectic in the alloy, the greater the impact of the construction of the eutectic on the properties of the alloy. Although the influence of the primary phase $\alpha(\text{Al})$ decreases in this situation, it should not be omitted [1]. Achieving an advantageous state of the structure of hypoeutectic Al-Si alloy therefore requires modifying the interaction involving the dendrite fragmentation of the primary $\alpha(\text{Al})$ phase and changing the morphology of the eutectic $\alpha(\text{Al}) + \beta(\text{Si})$.

Among the theories explaining the mechanism of refining the solid solution $\alpha(\text{Al})$, the three most-popular can be identified [2]:

- peritectic theory,
- boride theory,
- carbide theory.

According to the peritectic theory, $\alpha(\text{Al})$ phase refinement causes the elements that form along with aluminum peritectic systems, especially titanium, zirconium, and niobium. Fragmentation of the phase $\alpha(\text{Al})$ is the result of the peritectic reaction of the liquid metal with the primary phase Al_3Ti according to the following equation:



In boride theory, it is assumed that nucleation of the $\alpha(\text{Al})$ phase can be caused by both the TiB_2 boride and complex boride $(\text{Al,Ti})\text{B}_2$. The influence of $(\text{Al,Ti})\text{B}_2$ on the peritectic reaction [3] is also not excluded. Carbide theory binds the nucleation of the $\alpha(\text{Al})$ phase to carbides with regular and hexagonal structural networks (especially the TiC carbide). It is very interesting to see that one of the modified theories assumes that the Al_3Ti layer is formed on the TiB_2 boride particles directly or by the peritectic nucleation reaction of the primary $\alpha(\text{Al})$ phase.

The views on the eutectic silicon refining mechanism as a result of sodium or strontium modification make it possible to isolate two popular theories; one of which concerns nucleation, and the other involves silicon phase growth. In the first theory, it is assumed that [4] sodium and strontium impede the nucleation of eutectic silicon by neutralizing the AIP phase particles that play the role of an active silicon nucleus. This theory (called the theory of poisoning the nucleus) only explains the increased degree of supercooling the modified Al-Si alloys but does not address the fibrous morphology of eutectic silicon solidification.

The second theory [5] relates to the growth of eutectic silicon and takes into account the possibility of changing the kinetics of this growth (the so-called kinetic effect) as well as the ability to inhibit the growth of certain planes of silicon crystals. In the first case, it is assumed that the presence of such surface-active elements (such as sodium or strontium in front of the crystallization front) makes the diffusion of silicon into the planes of the growing crystal difficult. In the second case, it is assumed that there is an adsorption of the modifying element atoms on the surface of the crystal-liquid phase; this is assumed

to inhibit the growth of the privileged planes of silicon crystals for which the planes {111} are considered.

The developed dendritic structure of phase $\alpha(\text{Al})$ and lamellar eutectic silicon morphology limits the potentially achievable mechanical indexes of the AlSi11 alloy. This disadvantageous structure of silumin can be changed by applying a double modification, which involves the simultaneous addition that ensures a refinement of the dendrites of a constant solution of $\alpha(\text{Al})$ and additions that would change the morphology of the eutectic silicon from lamellar to fibrous [1, 6–8]. The authors have decided to check the suitability of AlB4 and AlSr10 pre-alloys for this purpose.

2. Description of research

Tests were carried out using the silumin AlSi11 of the following chemical composition: 11.8% Si; 0.16% Fe; 0.012% Zn; below 0.01% Mn and Cu; the rest Al. The melting and modification processes were carried out in a graphite-chamotte melting crucible in a furnace chamber.

The modification process was carried out by overheating the metal bath to a temperature of 1003K (730°C). The modifying additives included AlB4 and AlSr10 master alloys. The modification processes lasted ten minutes. The modification conditions as well as the results of the experiments are presented in Table 1.

Table 1. Influence of modifiers on mechanical properties of silumin AlSi11

No. of melt	Modifications conditions	Mechanical properties		
		R_{mT} MPa	A_{5T} %	HB
1	without modification	194	4.2	48
2	after modification with 0.25% AlSr10	209	7.4	51
3	after modification with 0.35% AlSr10	191	7.3	48
4	after modification with 0.25% AlB4	198	10.1	51
5	after modification with 0.35% AlB4	196	9.9	50
6	after modification with 0.30% AlB4 and 0.30% AlSr10	203	11.2	50
7*	after modification with 0.30% AlSr10	201	6.4	46
8**	after modification with 0.30% AlSr10	216	13	51
9**	after modification with 0.30% AlB4 and 0.30% AlSr10	212	6.8	48

* test samples were cast one hour after introducing modifier master alloy into liquid melt

** test samples were cast two hours after introducing modifier master alloy into liquid melt

In the case of the last three melts, the test samples were cast after one hour (7) and two hours (8 and 9) after the introduction of the modifiers to the liquid alloy.

The modification effects were evaluated based on macro- and microstructure changes and changes in the mechanical properties (R_m , A_5 , and HB) of silumin. The mechanical properties of silumin were investigated on specimens cast in chill according to Polish Standards (PN-65/H-88003).

In the unmodified state, the AlSi11 silumin was characterized by a coarse-grained macrostructure (Fig. 1a) and large eutectic silicon plates in the microstructure (Fig.1b). Modification of the alloy with 0.25% AlSr10 did not significantly change the macrostructure (Fig. 2a) but gives a good effect of the modification of eutectic $\alpha(\text{Al}) + \beta(\text{Si})$, which is a change in the eutectic morphology of silicon to fibrous (Fig. 2b). Increasing the amount of the AlSr10 additive to 0.35% did not change the structure of the silumin (Fig. 3a), but it ensured the improvement of the eutectic (Fig. 3b) while a few SrAl_4 phase particles appeared in the microstructure.

Modification of the AlSi11 silumin with 0.25% AlB4 (Fig. 4a) and 0.35% AlB4 (Fig. 5a) resulted in the very effective refinement of silumin grains without a noticeable change in the eutectic silicon morphology (Figs. 4b and 5b).

Simultaneous modification of the alloy with additions of 0.30% AlB4 and 0.30% AlSr10 (Fig. 6) resulted in the very efficient fragmentation of grains (Fig. 6a) and satisfactory refinement of the $\alpha(\text{Al}) + \beta(\text{Si})$ eutectics (Fig. 6b).

The sample of AlSi11 silumin cast after one hour after modification with 0.30% AlSr10 (Fig. 7) showed no significant effect of the modification on the macrostructure (Fig. 7a) and a good effect of the improvement of the $\alpha(\text{Al}) + \beta(\text{Si})$ eutectics. A similar effect of silumin modification was observed for the cast sample two hours after modification (Fig. 8). A sample of silumin modified simultaneously with the addition of 0.30% AlB4 and 0.30% AlSr10 showed a very strong fragmentation of the silumin grains (Fig. 9a) and a very good effect of the improvement of the $\alpha(\text{Al}) + \beta(\text{Si})$ eutectics (Fig. 9b). In the microstructure of this sample, a few particles of the SrAl_4 phase were observed.

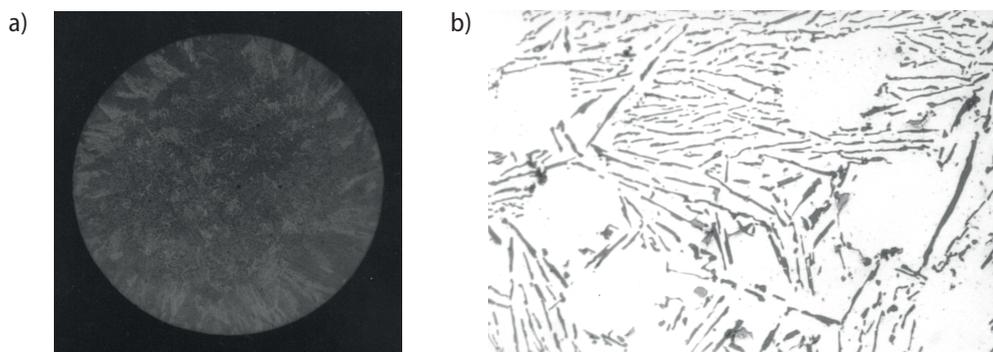


Fig. 1. Structure of silumin AlSi11 in non-modified state: a) macrostructure (magn. 1.5x); b) microstructure (magn. 500x)

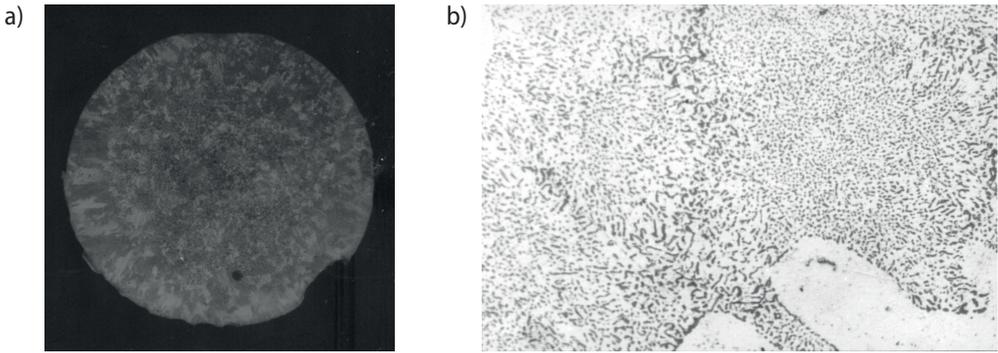


Fig. 2. Structure of silumin AlSi11 modified with addition of 0.25% AlSr10: a) macrostructure (magn. 1.5×); b) microstructure (magn. 500×)

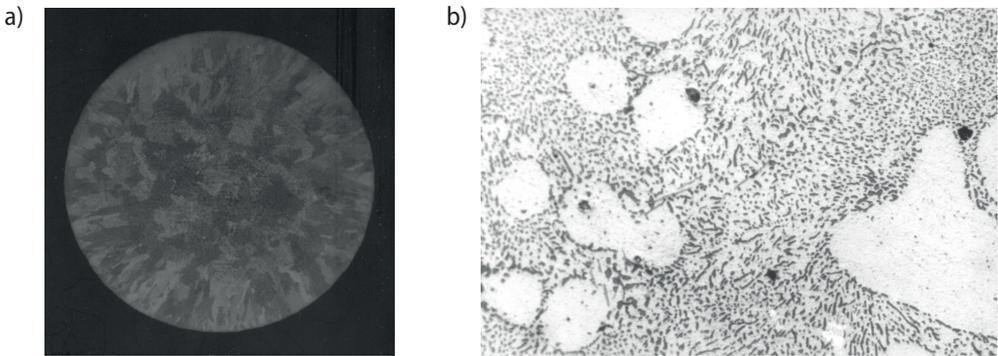


Fig. 3. Structure of silumin AlSi11 modified with addition of 0.35% AlSr10: a) macrostructure (magn. 1.5×); b) microstructure (magn. 500×)

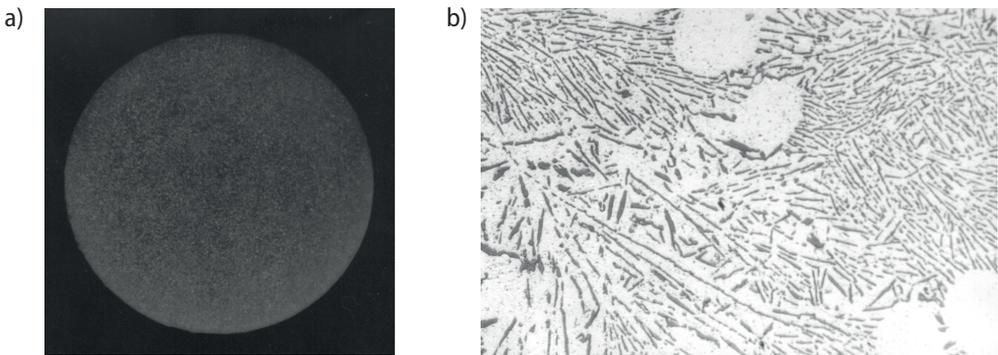


Fig. 4. Structure of silumin AlSi11 modified with addition of 0.25% AlB4: a) macrostructure (magn. 1.5×); b) microstructure (magn. 500×)

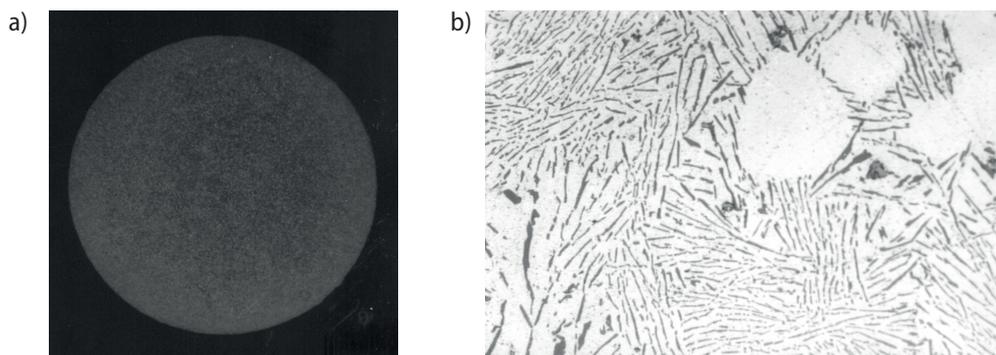


Fig. 5. Structure of silumin AlSi11 modified with addition of 0.35% AlB4: a) macrostructure (magn. 1.5×); b) microstructure (magn. 500×)

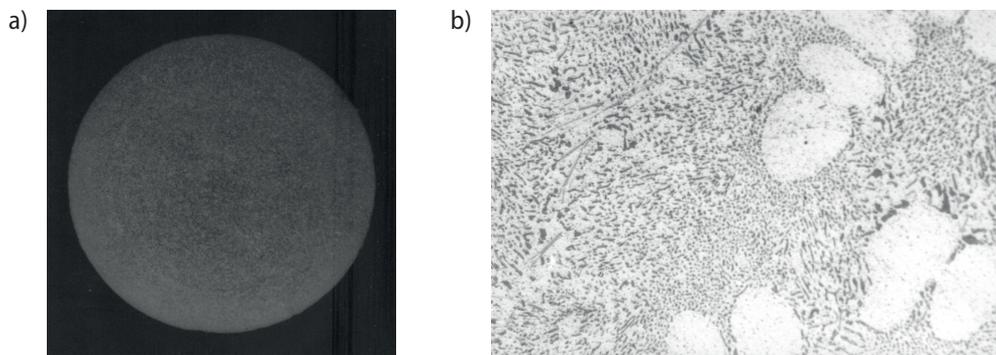


Fig. 6. Structure of silumin AlSi11 modified with additions of 0.30% AlB4 and 0.30% AlSr10: a) macrostructure (magn. 1.5×); b) microstructure (magn. 500×)

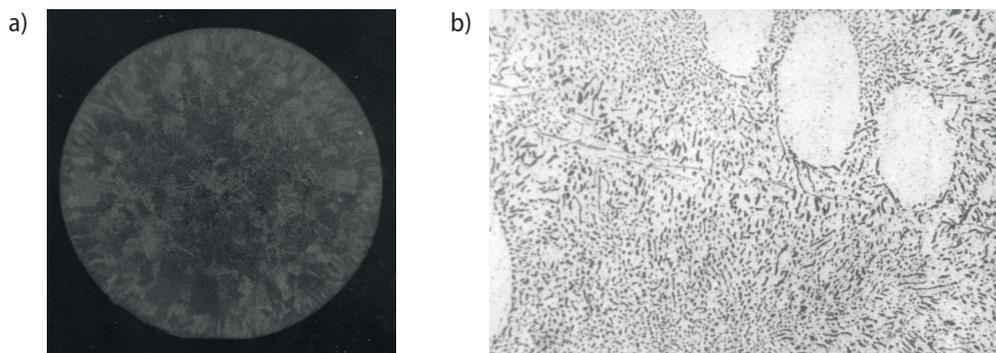


Fig. 7. Structure of silumin AlSi11 modified with addition of 0.30% AlSr10 cast one hour after modification: a) macrostructure (magn. 1.5×); b) microstructure (magn. 500×)

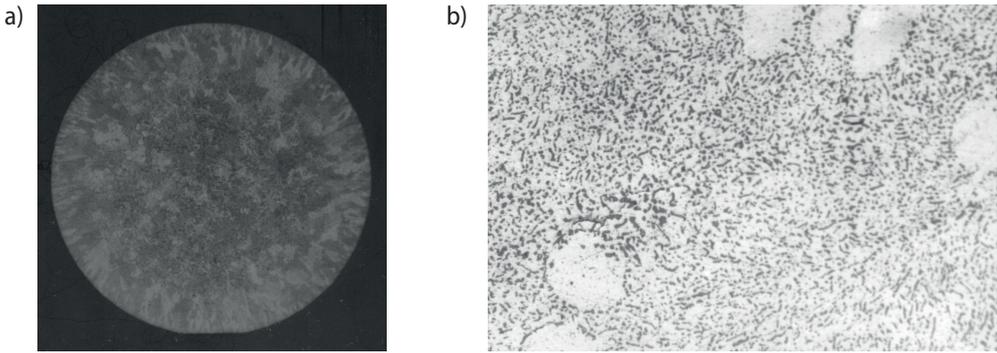


Fig. 8. Structure of silumin AlSi11 modified with addition of 0.30% AlSr10 cast two hours after modification: a) macrostructure (magn. 1.5×); b) microstructure (magn. 500×)

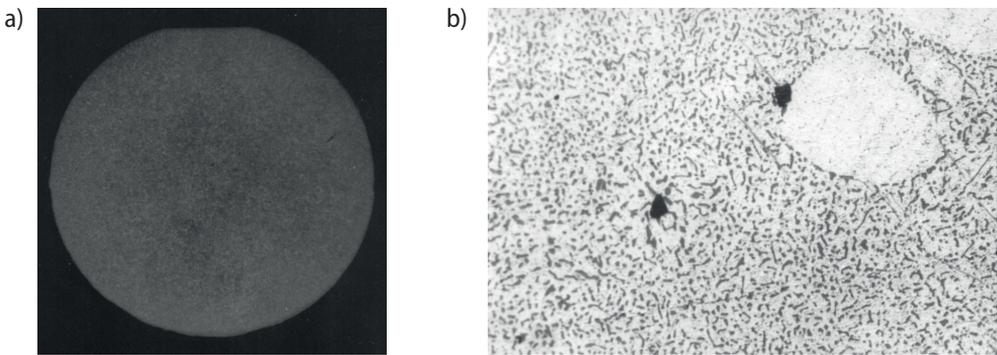


Fig. 9. Structure of silumin AlSi11 modified with additions of 0.30% AlB4 and 0.30% AlSr10 cast two hours after modification: a) macrostructure (magn. 1.5×); b) microstructure (magn. 500×)

Modification of the AlSi11 silumin in terms of structural changes caused changes in the mechanical properties (Tab. 1). Modification of the silumin by adding 0.25% AlSr10 (Melt 2) resulted in an increase in tensile strength R_m (from 194 MPa to 209 MPa), a simultaneous increase in relative elongation A_5 (from 4.2% to 7.4%), and a slight increase in hardness (from 48 HB to 51 HB). Increasing the amount of the AlSr10 additive to 0.35% (Melt 3) resulted in an increase of A_5 to 7.3% and a decrease of R_m to 191 MPa (so, to an R_m level similar to the unmodified silumin. This may be indicative of an excess of the modifier, which is confirmed by the presence of $SrAl_4$ phases in the microstructure of the silumin (Fig. 3b). Modification of the silumin with the addition of 0.25% and 0.35% AlB4 (Melts 4 and 5) resulted in an increase of the R_m alloy samples to 198 MPa and 196 MPa, respectively, with an increase of A_5 to 11.1% and 9.9%, respectively. These indexes provide the basis for the finding that an addition of 0.25% AlB4 is sufficient to refine AlSi11

silumin grains, a noticeable improvement in R_m , and a favorable A_5 change (more than double). The simultaneous modification of silicone with 0.30% AlB4 and 0.30% AlSr10 (Melt 6) resulted in an increase of R_m to 203 MPa and A_5 to 11.2%, with a slight increase in hardness to 50 HB.

Drawing the specimens of silumin modified with 0.30% AlSr10 after one hour after adding the modifier (Melt 7) showed a maintenance of R_m of 201 MPa with a satisfactory A_5 of 6.4%. The casting of samples of silumin modified with 0.30% AlSr10 after two hours after adding the modifier (Melt 8) provided a high R_m of 216 MPa with a very good level of A_5 of 13%. Modification of the silumin with 0.30% AlB4 and 0.30% AlSr10 (Melt 9) was carried out under similar conditions, providing a high R_m of 212 MPa with a satisfactory A_5 of 6.8%. The reduced elongation may be due to the presence of the $SrAl_4$ phase particles in the microstructure of the silumin (Fig. 9b).

Studies have shown that the AlSi11 alloy modified with an additive of strontium in the form of an AlSr10 master alloy ensured a good and lasting modification effect by enhancing by improvement of the $\alpha(Al) + \beta(Si)$ eutectic, resulting in an increase in the tensile strength R_m and more than double the increase in A_5 elongation while keeping the hardness at a similar level. Research has also shown that increasing the amount of the AlSr10 master alloy to 0.35% can result in the formation of $SrAl_4$ phase precipitation, which limits the effect of the modification, especially in terms of the impact on the tensile strength of the tested alloy.

Modification of AlSi11 silumin with a micro additive of boron in the form of an AlB4 master alloy results in a favorable increase (more than double) in the relative elongation of A_5 , but the increase in tensile strength is slight despite the fine fragmentation of the grains in the modified alloy.

Simultaneous modification of silumin with AlB4 and AlSr10 master alloys results in the strong grinding of silumin grains and satisfactory refinement of the $\alpha(Al) + \beta(Si)$ eutectic. As a result of this change in the structure of the silumin, the tensile strength and relative elongation are increased and maintained after the alloy has been held in a liquid state for two hours after adding the modifiers.

3. Conclusions

Modification of silumin AlSi11 with a micro additive of strontium in the form of an AlSr10 master alloy resulted in the improvement of eutectic $\alpha(Al) + \beta(Si)$ and a satisfactory increase in tensile strength and elongation after the addition of 0.25% of the modifier. Increasing the addition of 0.35% AlSr10 master alloy results in the formation of $SrAl_4$ phase precipitation resulting in no expected increase in R_m .

Modification of the AlSi11 alloy with a micro additive of boron in the form of an AlB4 master alloy in the amount of 0.25% results in the strong refinement of silumin grains and improvement of the relative elongation and a slight increase of R_m .

Modification of the AlSi11 silumin using AlB4 and AlSr10 master alloy additives simultaneously results in the high fragmentation of alloy grains and improvement of $\alpha(\text{Al}) + \beta(\text{Si})$ eutectics, which results in a substantial increase of R_m and A_5 in the tested alloy.

Modification of alloy AlSi11 with AlSr10 and a simultaneous modification with AlSr10 and AlB4 master alloys ensure a satisfactory increase in tensile strength R_m and relative elongation of A_5 by the casting of silumin samples after lasting two hours after the addition of modifiers.

References

- [1] Müller K.: Möglichkeiten der Gefügebeeinflussung eutektischer und naheutektischer Aluminium-Silizium-Gußlegierungen unter Berücksichtigung der mechanischen Eigenschaften. Doktor-Ingenieur Dissertation, Technische Universität Berlin, 1995
- [2] Körber K., Löhberg K.: Oberflächen- und Grenzflächenenergien von Aluminium-Silizium Schmelzen. Giesserei-Forschung, 23, 4 (1971), 173–177
- [3] Crosley P., Mondolfo L.F.: The Modification of Aluminum Silicon Alloys. Modern Casting, 49 (1966), 53–64
- [4] Hoefs P., Reif W., Schneider W.: Untersuchung einer neuen Kornfeinungsvorlegierung für Aluminium und Aluminium-Liegierungen. Giesserei, 12 (1994), 398–406
- [5] Kremer M.: Einfluß von Silizium auf die Kristallisation der α -Primärphase in unbehandelten und korngefeinten, untereutektischen Aluminium-Silizium-Liegierungen. Doktor-Ingenieur Dissertation. Technische Universität Berlin, 1996
- [6] Poniewierski Z.: Krystalizacja, struktura i właściwości siluminów. Wydawnictwa Naukowo-Techniczne, Warszawa 1989
- [7] Wasilewski P.: Siluminy – modyfikacja i jej wpływ na strukturę i właściwości. Krzepnięcie Metali i Stopów, Solidification of Metals and Alloys, Z. 21, Polska Akademia Nauk, Katowice 1993
- [8] Pietrowski S.: Siluminy. Politechnika Łódzka, Łódź, 2001